

# **AN EX VIVO MODEL USING HUMAN PERITONEUM TO EXPLORE MESH-TISSUE INTEGRATION**

Peter Falk, PhD<sup>1</sup>, Fernando Ruiz-Jasbon, MD<sup>1,2</sup>, Karin Strigård, Assoc Prof<sup>3</sup>,  
Ulf Gunnarsson, Prof<sup>3</sup> and Marie-Lois Ivarsson, Prof<sup>1</sup>

<sup>1</sup> Department of Surgery, Institute of Clinical Sciences, Sahlgrenska academy at  
University of Gothenburg, SE-416 85 Göteborg, Sweden.

<sup>2</sup> Hallands Hospital, SE-434 80 Kungälv, Sweden

<sup>3</sup> Department of Surgical and Perioperative Sciences, Umeå University, SE-901 85 Umeå,  
Sweden

## **Corresponding author:**

Peter Falk, PhD

Fibrinolysis Laboratory/Tissue Center, Department of Surgery, Sahlgrenska Academy,  
University of Gothenburg, Sahlgrenska University Hospital/Östra  
Diagnosvägen 11, SE-416 50 Göteborg, Sweden

Phone: (+46) 31-343 4970, Fax: (+46) 31-196317, e-mail: peter.falk@surgery.gu.se

Keywords: experimental model, peritoneum, peritoneal tissue, mesh, synthetic mesh,  
biocompatibility

## **Summary statement**

A human experimental model developed for long-term studies using peritoneal tissue to  
evaluate the integration with different materials, as synthetic meshes. This has, to our  
knowledge, not previously been demonstrated.

## ABSTRACT

Biological compatibility, in terms of implantation of foreign mesh material in hernia surgery, still needs experimental investigation. Present study develops an experimental model using human peritoneum to study the integration between tissue and different mesh material. The *ex vivo* model using peritoneal tissue was studied with different mesh material, and integration was monitored over time using microscopy.

It could be demonstrated that the peritoneal model may be kept viable in culture for several weeks. Cell migration was seen after 7-10 days in culture and could be further monitored over several weeks. The use of a human artificial model environment enabling the investigation of tissue/mesh integration has, to our knowledge, not been described previously.

This proof-of-concept model was developed, for the investigation of peritoneal biology and the integration between tissue and different mesh material. It has the potential to be useful in studies on other important biological mechanisms involving the peritoneum.

## INTRODUCTION

Most surgical repairs include use of meshes of different material, thereby introducing foreign material into the surgical field. It is well known that some meshes give rise to capsule formation while others are integrated into the surrounding connective tissue. Our knowledge about biological integration of meshes in terms of compatibility, tissue remodeling and repair is insufficient. One reason for this is the lack of human experimental models.

The peritoneum is a membrane covering an area of approximately 2m<sup>2</sup> in an adult person (diZerega, 2000, van der Wal and Jeekel, 2007) and has been the subject of investigation for decades. Our understanding of peritoneal healing and postoperative adhesion development due to altered fibrinolytic capacity is crucial and has previously been investigated using cultured mesothelial cells (Falk et al., 2013, Mutsaers and Wilkosz, 2007). It is unlikely that an experimental model using a monolayer of mesothelial cells is representative of the peritoneum in the surgical situation, since certain factors are missing or vary, in this case the connective tissue and the source of the cultured mesothelial cells. Healing and adaptation after surgery are complex mechanisms involving biological factors that are not fully understood. A preparation of intact peritoneal tissue, including the mesothelial layer and surrounding connective tissue with capillaries and lymphatic structures, might be a better alternative for the investigation of biological processes involving the peritoneum than a monolayer of cultured cells.

The role of peritoneum is central and studies on peritoneal healing includes not only aspects on tissue-mesh integration, but also the role of different surgical techniques, different mesh materials as well as the formation of adhesions. A human experimental *ex vivo* model might have the potential to facilitate further studies on these questions.

In the present study, we demonstrate an experimental *ex vivo* model using human peritoneal tissue to investigate the integration between human tissue and different prosthetic material.

## RESULTS AND DISCUSSION

### The *ex vivo* model

In the present study, we could demonstrate *ex vivo* cultures of adult human peritoneal tissue that remained viable for several weeks under controlled laboratory conditions (Fig. 1). To our knowledge this has not been achieved previously. This provides new and improved possibilities for studying biological interactions between peritoneum and different foreign materials used for implantation in novel and future surgical procedures.

By using inverted microscopy the peritoneal tissue could be monitored and documented with and without the presence of different meshes (Fig. 1D,E). The peritoneal tissue remained viable more than 26 days and in most cases longer than 30 days in culture, showing migrating peritoneal cells (Fig. 1F-H). Daily observation verified that there was no microscopic contamination in the culture medium and no signs of bacteria present in the bottom of the culture wells. Moreover, samples of medium taken for the detection of bacterial growth at Days 1 and 26 revealed no contamination.

In general, there is a lack of human experimental models focusing on the integration of implanted foreign mesh used in hernia surgery into the tissues of the human abdominal wall. Until now, most research has been done using experimental models in animals. Cobb et al presented a study on the strength of the abdominal wall after ventral hernia repair using different forms of polypropylene mesh in a porcine model (Cobb et al., 2006). Dolce et al investigated the formation of adhesions to different composite mesh material in a rabbit ventral hernia model (Dolce et al., 2012). A hernia model in rabbits was also the choice for Yeo et al in 2014, when the effectiveness of a synthetic bioabsorbable scaffold was further investigated (Yeo et al., 2014). In a clinical study on giant hernia in 2010, Johansson et al concluded that the postoperative strength of the abdominal wall muscles did not depend on the technique used for repair, and that the choice of surgical technique should be directed by anatomical circumstances (Johansson et al., 2011). However, the integration between tissue and implanted mesh material was not investigated in that study.

The use of dissected peritoneal tissue as an experimental model for studying the role of the peritoneum in gastric tumor cell dissemination in the abdominal cavity has been described previously (Cabourne et al., 2010). In that study, Cabourne et al could not keep their peritoneal tissue viable for more than 3-4 days in culture. However, in the present study we observed that viable cells continued to migrate into the peritoneal tissue after several weeks in culture. We cannot fully explain the reason for the differences between Cabourne's results and the present study. Still, there are differences in the handling of the peritoneal tissue since Cabourne used sodium chloride as transport medium from the operation theater to the laboratory (Cabourne et al., 2010), whilst culture medium at normal pH was used in the present study. The use of sodium chloride in surgery for rinsing the abdominal cavity has been the subject of discussion since it has a low pH if not buffered (Polubinska et al., 2006) and it has also been considered cytotoxic in models using cultured cells (Polubinska et al., 2008). These differences may be of limited significance but should be noted.

Peritoneal healing and repair has been described for many years but only in recent decades has our understanding of the mechanisms regulating this process become more established. The principles of mesothelial remodeling and regeneration differ from the repair of traditional wound healing (Mutsaers et al., 2007, Mutsaers, 2002). Mesothelial differentiation is one important part in peritoneal remodeling that occurs even in culture under certain conditions such as stimulation by growth factors (Yang et al., 2003, Falk et al., 2013, Falk et al., 2008). When peritoneal tissue is cultured over a longer period of time it is likely to believe that there is a certain progress of differentiation in the cultured cells. Cell differentiation might have taken place in the present study, as indicated by the structural changes in peritoneal tissue seen over time, but this was not further investigated.

Peritoneal healing and mechanisms for development of adhesions are crucial after abdominal surgery. Due to differences in fibrinolytic capacity resulting in an imbalance in fibrin formation and fibrin degradation, there are possibilities for creating post-operative adhesions (Falk et al., 2013, Mutsaers and Wilkosz, 2007). Some of the

involved factors present in the peritoneal tissue might be possible to further investigate using a peritoneal *ex vivo* model, in contrast to culture mesothelial cells only.

Furthermore, not to jeopardize the healing properties of the donor's parietal peritoneum, thereby introducing an ethical dilemma, the peritoneal tissue used in the present study was taken from the part of the inguinal hernia sac that had been removed. *In vivo* data support the notion that mesothelial proteins secreted at different anatomical sites are similar (Serre et al., 2003) but that healing properties may vary. Also, when obtaining peritoneal samples, gentle handling with sharp dissection, without electrocoagulation or other energy emitting devices, was employed. Histology specimens of the sampled peritoneal tissue confirmed several layers in the tissue, including mesothelial cells and visible capillaries (Fig. 1I). Despite this, tissue with an intact mesothelial surface and totally free from damage from the surgical procedure could not be guaranteed. This also applies to the stress affected part of the peritoneum and possible damage to phospholipid layers present in the mesothelial cell membrane, such as hyaluronic acid or glycosaminoglycans (Mutsaers and Wilkosz, 2007).

### ***Ex vivo* model in the presence of synthetic mesh**

When synthetic mesh was incubated together with the peritoneal tissue, as illustrated (Fig. 2 and 3A,B), all the *ex vivo* models with a mesh could be kept in culture for 26 days, and some were kept for 56 days without any sign of bacterial contamination (Fig. 2). Further experiments, including monitoring and photographic documentation, were performed using the Bard Soft Mesh. Time lapses of the *ex vivo* model with or without mesh, were used to monitor cell coverage over time. The primary coverage of cells from the peritoneal tissue and adaptation into the mesh could be seen after approximately one week (Day 7). Single cells began to migrate towards the foreign material and this escalated with time (Fig. 3A,B).

Between Days 17 and 28 more activity was seen in the model illustrated by an increase in cell count and amount of migrating cells. By day 48 large areas of the synthetic mesh were covered with fibroblasts migrating from the peritoneal tissue.

Migrating cells finally found in the cell culture bottom was later found to be fibroblasts verified by morphological appearance and growth characteristics (Fig. 3C). No

differences were seen in cell count, cell activity or viability between the *ex vivo* models with and without synthetic mesh, nor was any difference seen between the two different types of mesh in the present study.

Sotiri et al reviewed the problems concerning adhesion to foreign materials used in medicine by investigating the use of immobilized liquid layers as an approach to decrease tissue adhesion to medical devices (Sotiri et al., 2016). In order to further understand the integration between tissue and foreign materials, Whelove et al in 2011 presented a new technique adding nanoparticles covered with gold to improve biocompatibility (Whelove et al., 2011). They used nanoparticle-covered polyethylene mesh in their *in vitro* experiments, showing improved adhesion of L929 fibroblasts and decreased bacterial adhesion to the synthetic mesh. The fact that their experimental model was an *in vitro* rather than an *ex vivo* model meant that a simple monolayer of cultured cells was used as opposed to an intact part of an organ as in the present study using peritoneum.

In the present experimental *ex vivo* model, two types of synthetic meshes were used, one synthetic non-absorbable and one synthetic absorbable version. The main requisite is that the mesh must be semi-transparent to enable transmission of light using inverted microscopy. In future experimental models comparisons will be performed between other types of mesh, both synthetic and biological. Other types of visualization systems will then be used.

In summary, we have developed a proof-of-concept model of adult human peritoneal tissue, for the investigation of peritoneal biology and the incorporation of foreign mesh material. *Ex vivo* peritoneal preparations could be kept viable under controlled laboratory conditions for up to 56 days, and this, to our knowledge, has not previously been described.

The present *ex vivo* model has the potential to become an important research tool for studies on the peritoneum or areas of research where the peritoneal membrane is a key component. Furthermore, this model provides new possibilities for studying biological integration between tissue and potential novel materials for implantation in future surgical procedures, in both human and other mammals.

## MATERIALS AND METHODS

If not otherwise stated, all chemicals and cell culture reagents were purchased from Sigma-Aldrich (St Louis, Mo, USA).

### The *ex vivo* peritoneal model

After having gained informed consent, peritoneal tissue was isolated, from totally five patients undergoing routine surgery for inguinal hernia repair. Fresh tissue samples were placed in a sterile bowl and submerged in sterile culture media E199 (Sigma-Aldrich). Within 5 minutes the sterile bowl was transported from the operation theatre to the laboratory where the tissue was immediately dissected to remove extra-peritoneal fat. The samples were then cut into squares approximately 25 mm x 25 mm to be mounted in the *ex vivo* model as described (Fig. 1). Depending on variation in size of the peritoneal tissue extracted, different amount of experimental setups were obtained. A total of eight (8) experimental set-ups were performed (3 without mesh, 3 with Bard Soft mesh, 2 with TIGR Matrix, each set-up performed as a duplicate (Fig. 2). Carefully avoiding damage to the mesothelial surface, the tissue was gently suspended between two acrylic rings with the mesothelial cell surface pointing upwards, and submerged in culture medium in a 6-well culture dish without touching the cell culture plate. Culture medium (E199) supplemented with 30 IU/mL penicillin and streptomycin (PEST), 1.1 mM L-glutamine, 20% fetal calf serum (FCS), 0.5 µg/mL hydrocortisone, 50 µg/mL growth factor according to Maciag et al (Maciag et al., 1979) and 10 IU/mL heparin (Leo Pharma, Malmö, Sweden) was used as described previously (Reijnen et al., 2001, Falk et al., 2013). The *ex vivo* model specimens were cultured in a CO<sub>2</sub> incubator (Forma, Ninolab, Upplands Väsby, Sweden) at 37°C with 5% carbon dioxide. The culture medium was completely changed three times a week (Fig. 1).

All handling in the cell culture laboratory was performed under sterile conditions in the area of a laminar-air-flow (LAF) unit (Holten, Ninolab, Upplands Väsby, Sweden). Monitoring of changes in the experimental model was performed using inverted phase-contrast microscopy and photographic documentation (Axiovert 25 and Axiovision, Carl-Zeiss Gmbh, Jena, Germany). Repeated photographic documentations of the experimental set-ups were performed individually and consecutively every second or



third day until each set-up was completed. Each experiment was performed in duplicates in two or three independent experiments.

### **Viability of peritoneal tissue, and bacterial contamination**

Regular monitoring of the *ex vivo* specimens was performed, including the observation of any living cells being exfoliated from the isolated peritoneal tissue. No sign of contamination was seen in the culture medium or tissue during the first days of culture in the *ex vivo* model. Samples were also taken for detection of bacterial contamination of the medium at Days 1 and 26. Monitoring and photographic documentation were performed using inverted microscopy and the Axiovision system (Carl-Zeiss).

### **Using the *ex vivo* model in the presence of synthetic mesh**

In order to investigate integration between peritoneal tissue and foreign material, different types of mesh were placed on both the inside (mesothelial side) and outside (retroperitoneal side) of the peritoneal preparations produced in the *ex vivo* model described above. A large-pore monofilament polypropylene mesh (Bard Soft Mesh, Bard Davol Inc, Warwick, RI, USA) and an absorbable synthetic mesh (TIGR Matrix/Surgical mesh, Novus Scientific, Uppsala, Sweden) were investigated.

## **Ethics**

The sampling of peritoneal tissue was conducted with the human subjects understanding and consent and was approved by the Local Ethics Committee (University of Gothenburg, Dnr: Ö728-03).

## **Acknowledgements**

To Dr Peter Cox for providing language help.

## **Competing interests**

The authors declare no competing or financial interests.

## **Author contributions**

All authors participated in the design, interpretation of the experimental studies and analysis of the data and review of the manuscript; PF and FRJ conducted the experiments, PF and M-LI wrote the main parts of the manuscript, and UG and KS contributed with valuable layout and language review and editing.

## **Funding**

The project was supported using grants from the Swedish LUA/ALF Foundation (ALFGBG-143521), from FoUU, Region Halland, Sweden and from the Swedish Cancer Society (Ref No: 130355).


## REFERENCES

- Cabourne, E. J., Roberts, G., Goldin, R., Ryder, T., Mobberly, M. & Ziprin, P. (2010). Investigation of tumor-peritoneal interactions in the pathogenesis of peritoneal metastases using a novel ex vivo peritoneal model. *J Surg Res*, 164: e265-72.
- Cobb, W. S., Burns, J. M., Peindl, R. D., Carbonell, A. M., Matthews, B. D., Kercher, K. W. & Heniford, B. T. (2006). Textile analysis of heavy weight, mid-weight, and light weight polypropylene mesh in a porcine ventral hernia model. *J Surg Res*, 136: 1-7.
- Dizerega, G. S. 2000. Peritoneum, peritoneal healing, and adhesion formation, New York, Springer Verlag.
- Dolce, C. J., Keller, J. E., Stefanidis, D., Walters, K. C., Heath, J. J., Lincourt, A. L., Norton, H. J., Kercher, K. W. & Heniford, B. T. (2012). Evaluation of soft tissue attachments to a novel intra-abdominal prosthetic in a rabbit model. *Surg Innov*, 19: 295-300.
- Falk, P., Angenete, E., Bergstrom, M. & Ivarsson, M. L. (2013). TGF-beta1 promotes transition of mesothelial cells into fibroblast phenotype in response to peritoneal injury in a cell culture model. *Int J Surg*, 11: 977-82.
- Falk, P., Bergstrom, M., Palmgren, I., Holmdahl, L., Breimer, M. E. & Ivarsson, M. L. (2008). Studies of TGF-beta(1-3) in Serosal Fluid During Abdominal Surgery and Their Effect on In Vitro Human Mesothelial Cell Proliferation. *J Surg Res*.
- Johansson, M., Gunnarsson, U. & Strigard, K. (2011). Different techniques for mesh application give the same abdominal muscle strength. *Hernia*, 15: 65-8.
- Maciag, T., Cerundolo, J., Ilsley, S., Kelley, P. R. & Forand, R. (1979). An endothelial cell growth factor from bovine hypothalamus: identification and partial characterization. *Proc Natl Acad Sci U S A*, 76: 5674-8.
- Mutsaers, S. E. (2002). Mesothelial cells: their structure, function and role in serosal repair. *Respirology*, 7: 171-91.


- Mutsaers, S. E., Prele, C. M., Lansley, S. M. & Herrick, S. E. (2007). The origin of regenerating mesothelium: a historical perspective. *Int J Artif Organs*, 30: 484-94.
- Mutsaers, S. E. & Wilkosz, S. (2007). Structure and function of mesothelial cells. *Cancer Treat Res*, 134: 1-19.
- Polubinska, A., Breborowicz, A., Staniszewski, R. & Oreopoulos, D. G. (2008). Normal saline induces oxidative stress in peritoneal mesothelial cells. *J Pediatr Surg*, 43: 1821-6.
- Polubinska, A., Winckiewicz, M., Staniszewski, R., Breborowicz, A. & Oreopoulos, D. G. (2006). Time to reconsider saline as the ideal rinsing solution during abdominal surgery. *Am J Surg*, 192: 281-5.
- Reijnen, M. M., Van Goor, H., Falk, P., Hedgren, M. & Holmdahl, L. (2001). Sodium hyaluronate increases the fibrinolytic response of human peritoneal mesothelial cells exposed to tumor necrosis factor alpha. *Arch Surg*, 136: 291-6.
- Serre, V., Tezenas Du Montcel, S., Kontula, L., Simon, M., Perret, E., Nedellec, P., Vicart, P. & Duron, J. J. (2003). In vivo protein markers of human peritoneal mesothelial cells: do they differ according to their anatomical sites? *Eur J Surg Suppl*: 40-5.
- Sotiri, I., Overton, J. C., Waterhouse, A. & Howell, C. (2016). Immobilized liquid layers: A new approach to anti-adhesion surfaces for medical applications. *Exp Biol Med (Maywood)*, 241: 909-18.
- Van Der Wal, J. B. & Jeekel, J. (2007). Biology of the peritoneum in normal homeostasis and after surgical trauma. *Colorectal Dis*, 9 Suppl 2: 9-13.
- Whelove, O. E., Cozad, M. J., Lee, B. D., Sengupta, S., Bachman, S. L., Ramshaw, B. J. & Grant, S. A. (2011). Development and in vitro studies of a polyethylene terephthalate-gold nanoparticle scaffold for improved biocompatibility. *J Biomed Mater Res B Appl Biomater*, 99: 142-9.
- Yang, A. H., Chen, J. Y. & Lin, J. K. (2003). Myofibroblastic conversion of mesothelial cells. *Kidney Int*, 63: 1530-9.

Yeo, K. K., Park, T. H., Park, J. H., Chang, C. H., Kim, J. K. & Seo, S. W. (2014).  
Histologic changes of implanted gore bio-a in an experimental animal model.  
Biomed Res Int, 2014: 167962.


## FIGURES

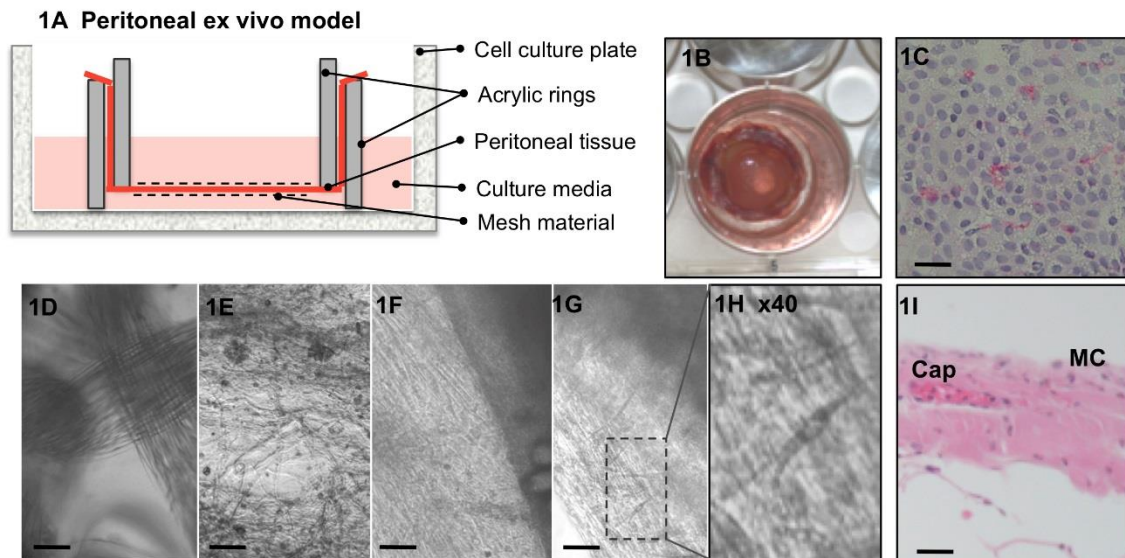

**Fig. 1: The ex vivo model using human peritoneal tissue.** During sterile conditions the peritoneal tissue is fitted between two acrylic rings (1A) and placed into a cell culture well enabling an inside and an outside of the peritoneal membrane (1B). An imprint of the peritoneal tissue using glass slides, confirms the present layer of mesothelial cells using htx/eosin staining of an “en face” *häutchen* preparation (1C). Using inverted light microscopy the peritoneal membrane could be monitored and documented with (1D) and without (1E) the presence of a mesh. After 7 to 10 days in culture, cells in the peritoneal tissue, starts to migrate to the foreign synthetic mesh (Bard Soft) (1G,H). These migrating cells could not be seen at day 3 in the ex vivo model (1F). Histology confirm several layers of the peritoneal tissue used (1I) MC=Mesothelial layer, Cap= capillary with endothelial cells (Scale bar =100 $\mu$ m).

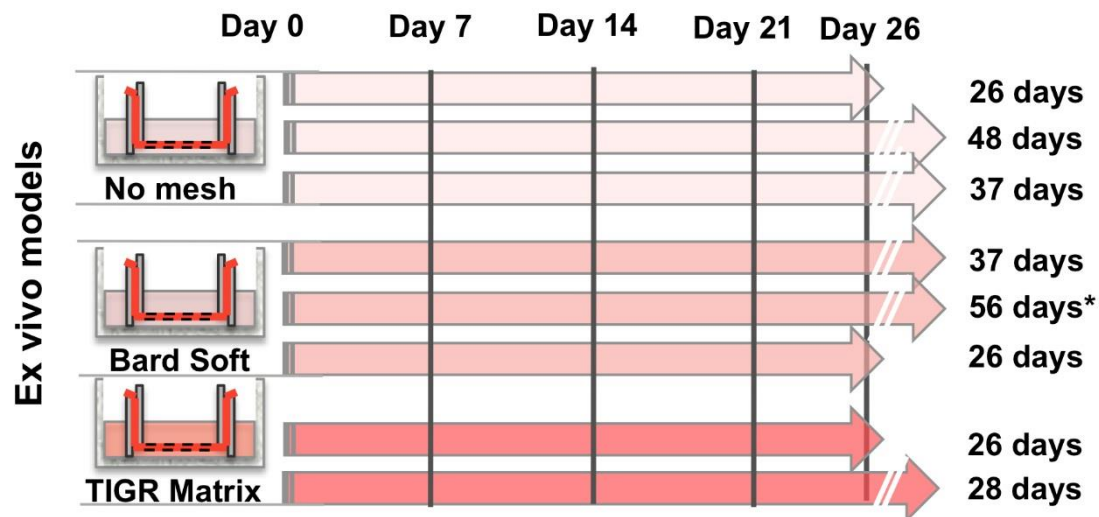

**Fig. 2: Summary of performed experiments.** Together with the peritoneal tissue alone, two different synthetic meshes (Bard Soft and TIGR Matrix) were investigated for at least 26 days. Each arrow indicates a duplicate of experimental set-ups (n=2-3) of ex vivo models (n=4-6 for each group). \*= 1 (of 2) set ups was discarded after 60 days in culture due to possible ocular bacterial contamination. Samples from the conditioned culture media revealed no bacterial contamination.

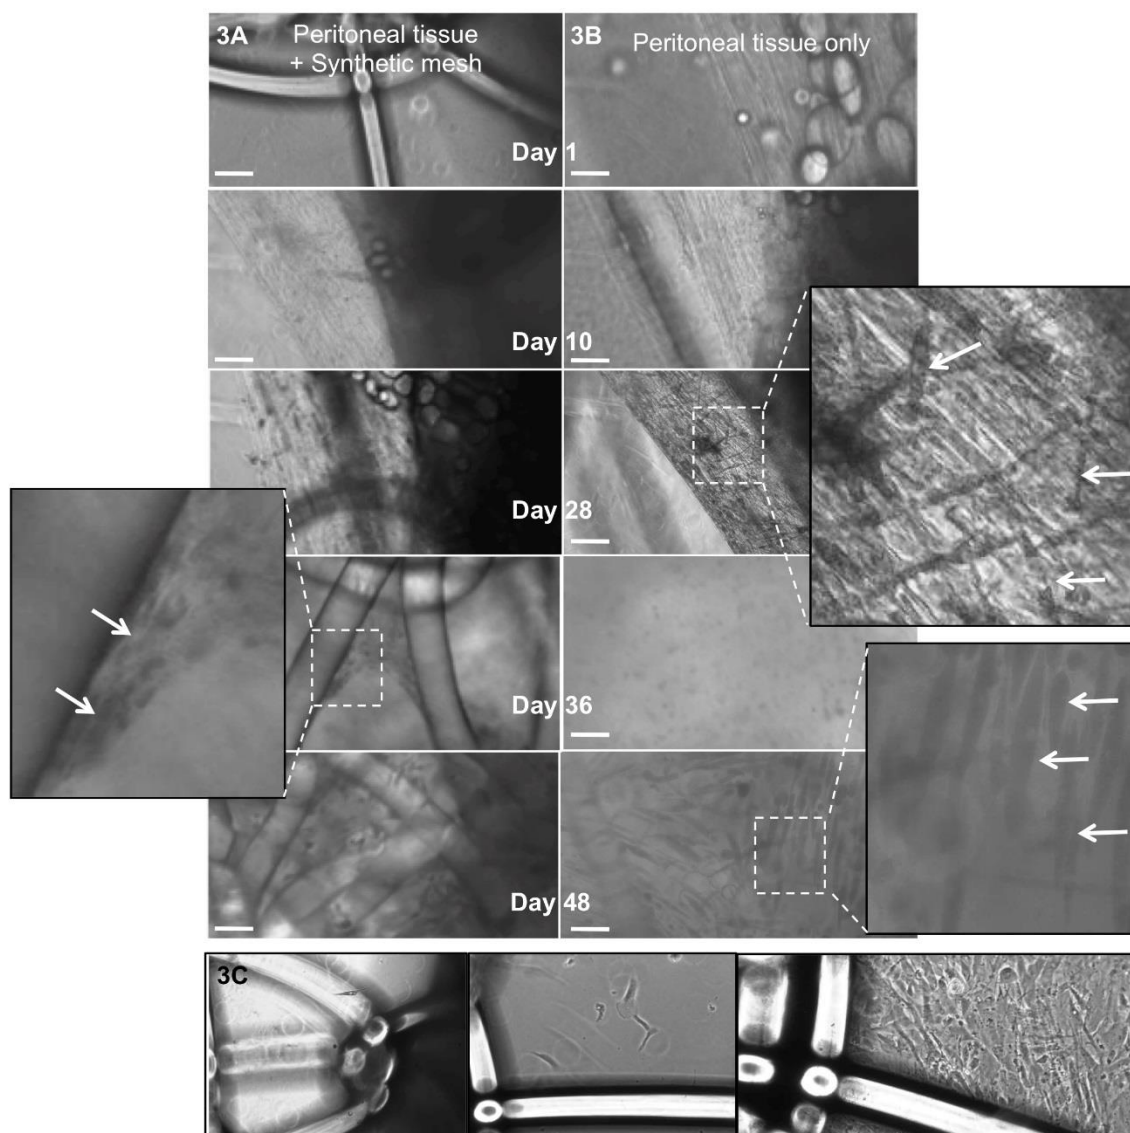

**Fig. 3: Time lapse of the *ex vivo* peritoneal tissue model during culture, with and without the presence of a synthetic mesh.** The peritoneal tissue could be kept in culture up to 56 days without bacterial contamination. Cells migrating from the peritoneal tissue could be monitored from Day 10 onwards (white arrows). No differences in cell migration or cell count were seen with or without the presence of the synthetic mesh (3A,B). Migrating cells found in the bottom of the chamber/well was verified to be fibroblasts by their growth and morphological characteristics (3C) (Scale bar =100 $\mu$ m).